



**HERCULUX**  
恒坤光电

Chengdu HercuLux Photoelectric  
Technology Co.,Ltd  
**Product Approval**

Approval number :

Customer :

Manufacturer : Chengdu HercuLux Photoelectric Technology Co.,Ltd

PN	Code	Product
HK-110@32-15-D14-20-1g-1	1. 01. 02312	HK 110@32-15° lens
HK-110@32-24-D14-20-1g-2	1. 01. 02313	HK 110@32-24° lens
HK-110@32-36-D14-20-1g-1	1. 01. 92129	HK 110@32-36° lens
HK-110@32-60-D14-20-1g-1	1. 01. 92091	HK 110@32-60° lens



Supplier confirmation				Client confirmation			
Proposed		DATE		Qualified <input type="checkbox"/>		DATE	
Project manager		DATE		Unqualified <input type="checkbox"/>		DATE	
Audit		DATE		Audit		DATE	
Approved		DATE		Approved		DATE	
Stamp		DATE		Stamp		DATE	

( Confirmation of acceptance by both parties must be signed and sealed )

Factory: Chengdu Shuangliu District, Iot industrial park 2 road HercuLux Photoelectric Park

Phone : 028-85887727 ( 801 ) 028-85887990 ( 801 )

Fax : 028-85887730

www.hkoptics.com

Sales Dept: Shenzhen Nanshan District Nanshan Cloud Valley Innovation Industrial Park Comprehensive Service Building,

TEL: 0755-2937 1541

FAX: 0755-2907 5140

\*Approval In duplicate , for both supplier and customer.



**HERCULUX**  
恒坤光电

# Product Approval


TEL: 0755-2937 1541

FAX: 0755-2907 5140

www.hkoptics.com

Date updated: 2020/11/6

Product Picture:	
PN:	HK-110@32-15-D14-20-1g-1
Size(L*W*H/ $\Phi$ *H):	$\Phi$ :110mm; H:32mm
Material:	PC
Efficiency:	\
Temperature(Topr):	-40°C to +120°C
FWHM:	15°、24°、36°、50°
Matched LES:	D14

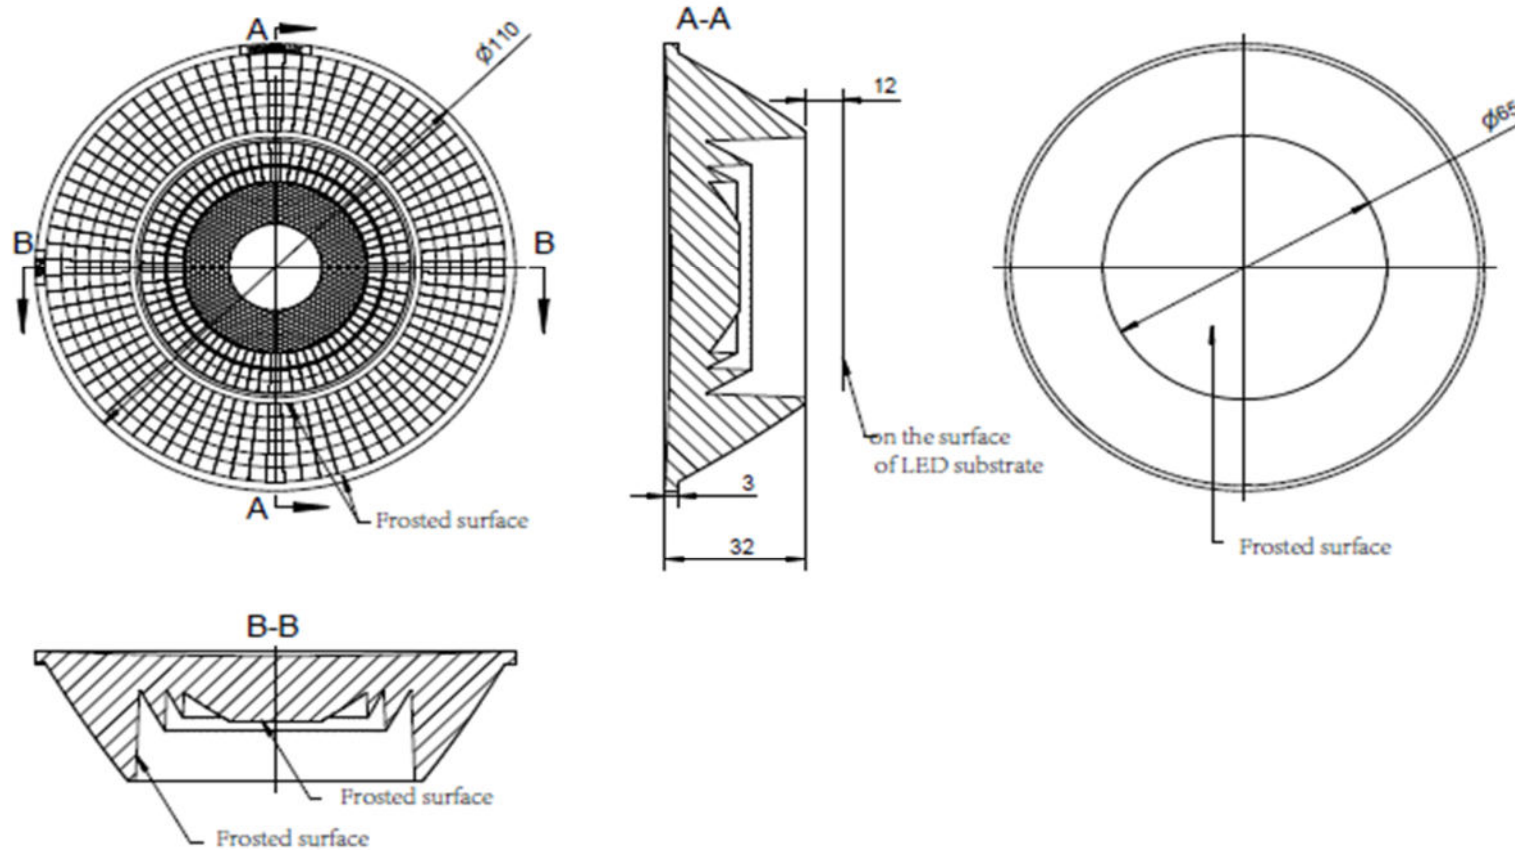


**Technical remark:**

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.

Optical design			HK-110@32-15-D14-20-1g-1	
Structure design			HK 110@32-15 <sup>g</sup> lens	
Review			1.01.02312	
Validation			Material:	PC
				CDHK

MT5 Tolerance table (mm)	Basic size	<3	3~10	24~65	65~140	140~250	250~450	>450
		Tolerance value	±0.1	±0.15	±0.35	±0.50	±0.80	±1.2

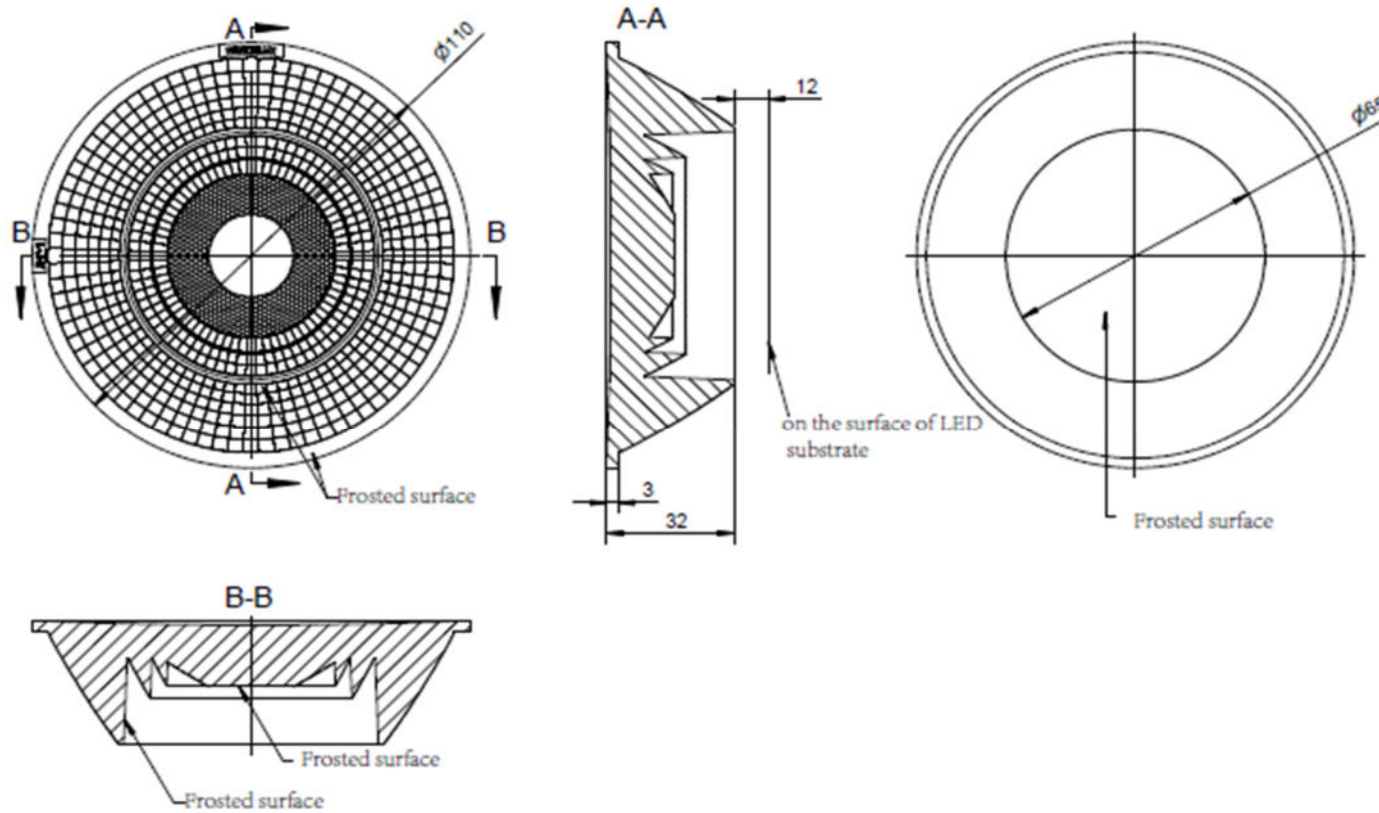


**Technical remark:**

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.

Optical design			HK 110@32-24 <sup>g</sup> lens		HK-110@32-24-D14-20-1g-2		
Structure design			HK 110@32-24 <sup>g</sup> lens		1.01.02313		
Review					Number of drawing	qty	weight
Validation			Material:	PC	CDHK		

MT5 Tolerance table (mm)	Basic size	<3	3~10	24~65	65~140	140~250	250~450	>450	
	olerance value	±0.1	±0.15	±0.35	±0.50	±0.80	±1.2	±2.0	

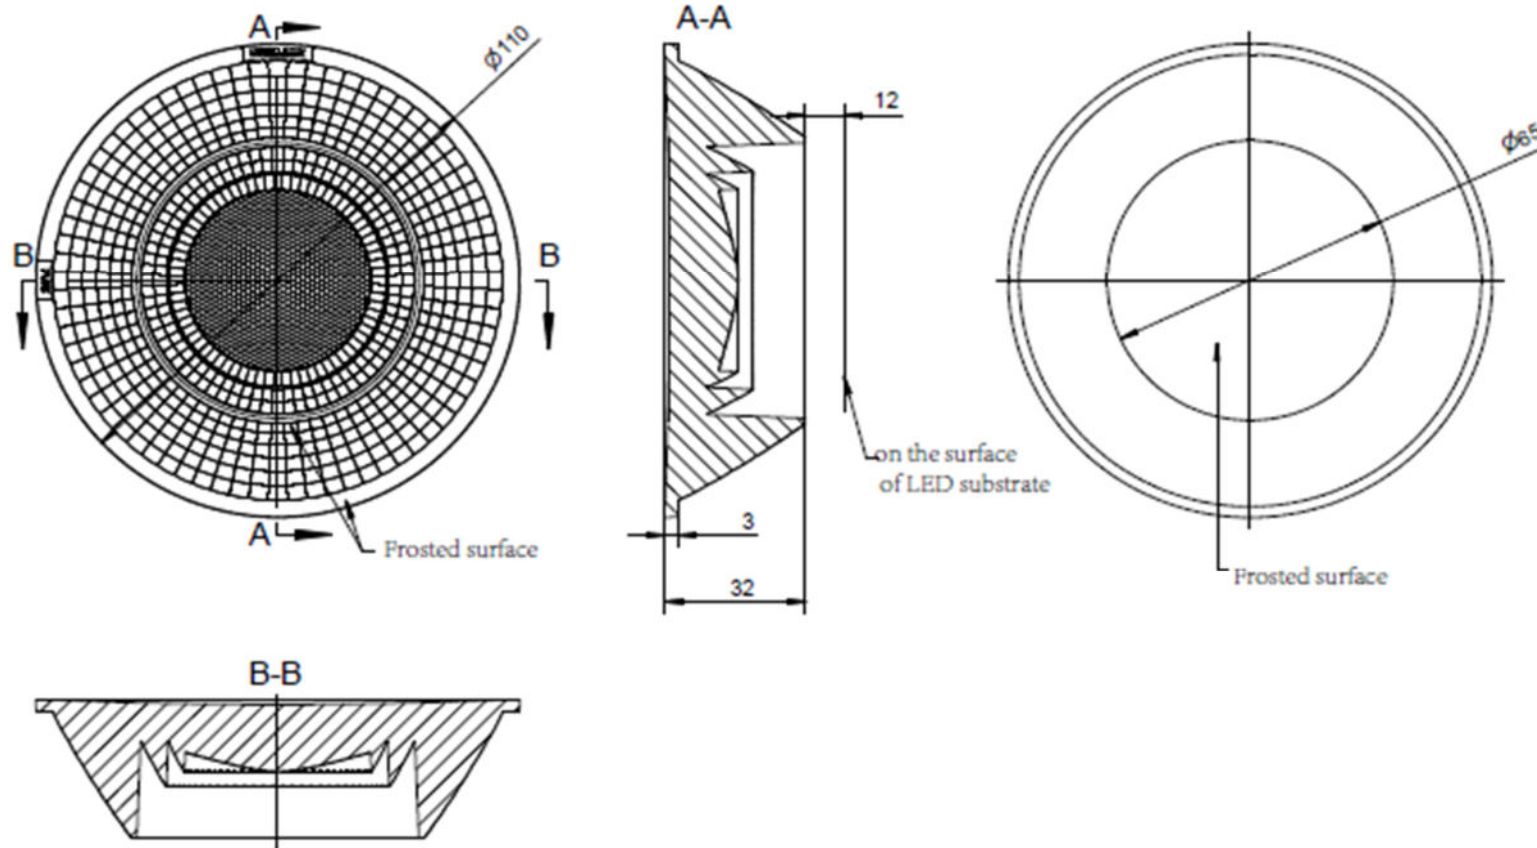


**Technical remark:**

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.

Optical design			HK 110@32-36 <sup>g</sup> lens			HK-110@32-36-D14-20-1g-1		
Structure design						1.01.92129		
Review			Number of drawing		qty	weight		
Validation			Material:	PC		CDHK		

MT5 Tolerance table (mm)	Basic size	<3	3~10	24~65	65~140	140~250	250~450	>450
	olerance valu	±0.1	±0.15	±0.35	±0.50	±0.80	±1.2	±2.0

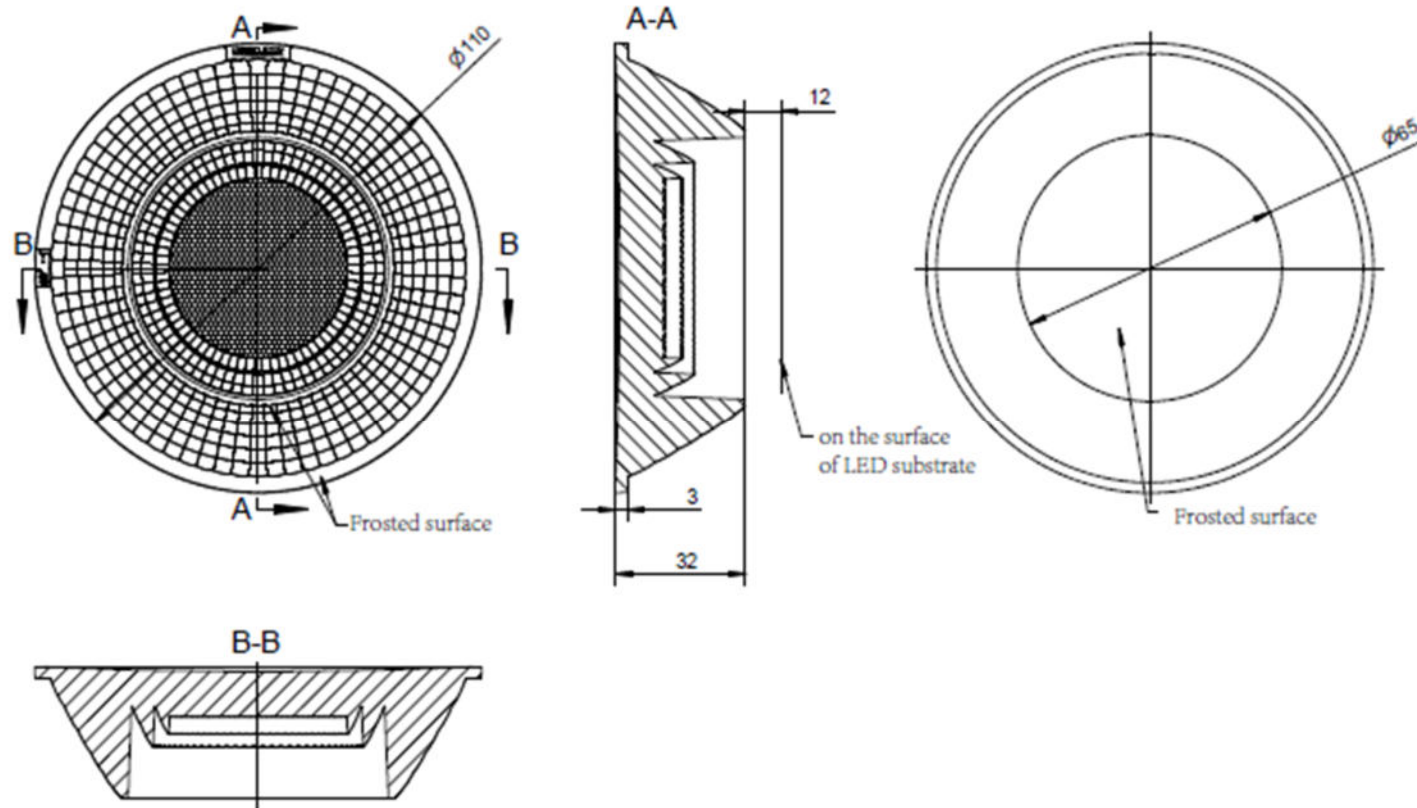


**Technical remark:**

1. The 3D map is not indicated for rounded corners and draft angle.
2. The dimensional tolerances are not specified according to GB/T 14486 2008 MT5.
3. The surface has no flash, shrinkage, bubbles and other defects.

Optical design			HK 110@32-60° lens		HK-110@32-60-D14-20-1g-1		
Structure design					1.01.92091		
Review				Number of drawing	qty	weight	
Validation			Material:	PC	CDHK		



MT5 Tolerance table (mm)	Basic size	<3	3~10	24~65	65~140	140~250	250~450	>450	
	olerance valu	±0.1	±0.15	±0.35	±0.50	±0.80	±1.2	±2.0	



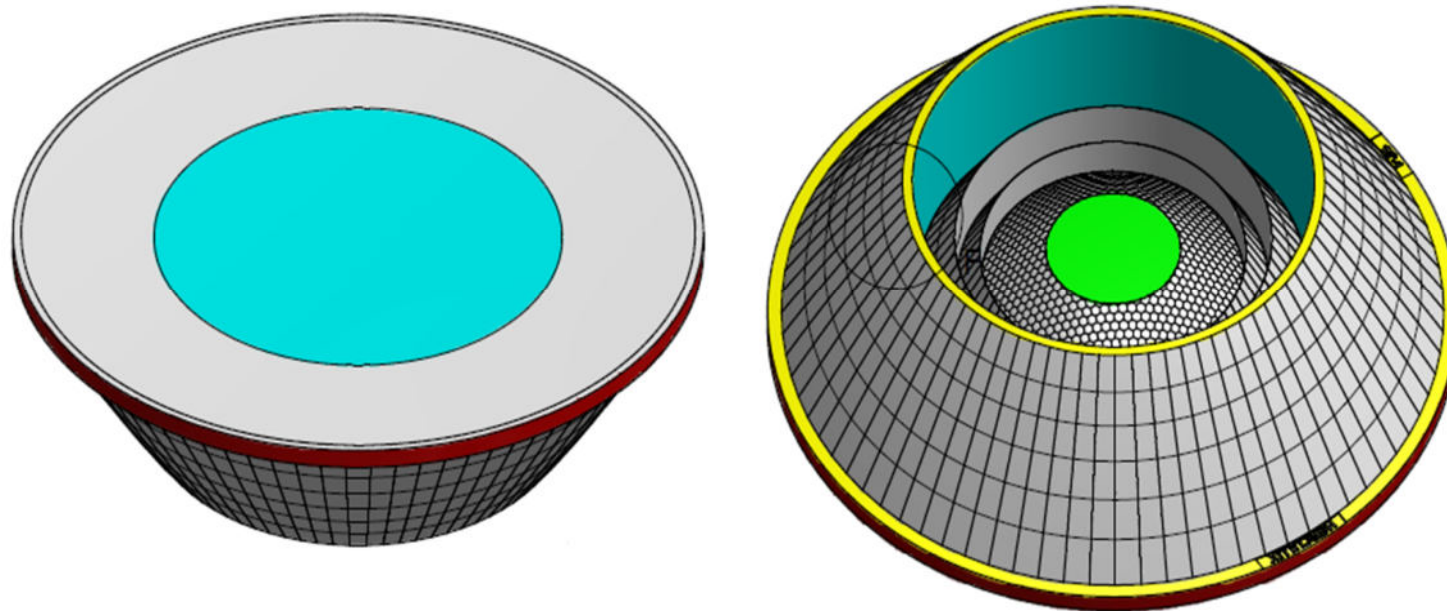





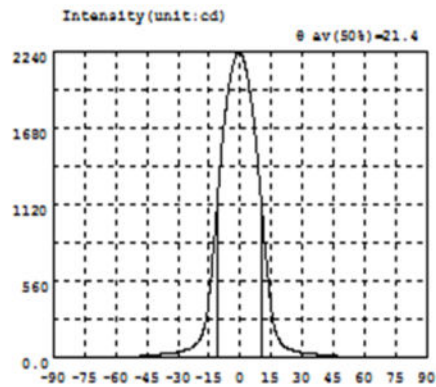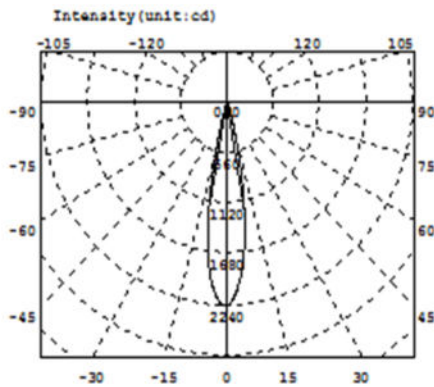

Intensity data:(deg , cd) C0-180



A	I	A	I	A	I	A	I	A	I	A	I
-90.0	0.2825	-58.5	7.292	-27.0	56.49	4.5	1950	36.0	28.70	67.5	4.385
-88.5	0.3060	-57.0	7.948	-25.5	63.73	6.0	1785	37.5	26.40	69.0	4.051
-87.0	0.4661	-55.5	8.668	-24.0	72.65	7.5	1578	39.0	23.97	70.5	3.730
-85.5	0.7054	-54.0	9.485	-22.5	85.34	9.0	1334	40.5	22.46	72.0	3.417
-84.0	1.022	-52.5	10.31	-21.0	104.9	10.5	1065	42.0	20.49	73.5	3.086
-82.5	1.358	-51.0	11.37	-19.5	137.8	12.0	796.9	43.5	18.49	75.0	2.734
-81.0	1.683	-49.5	12.28	-18.0	194.4	13.5	549.0	45.0	16.09	76.5	2.374
-79.5	1.998	-48.0	13.77	-16.5	267.9	15.0	341.7	46.5	14.20	78.0	2.003
-78.0	2.303	-46.5	15.35	-15.0	457.8	16.5	217.2	48.0	12.70	79.5	1.653
-76.5	2.591	-45.0	17.71	-13.5	692.5	18.0	151.7	49.5	11.52	81.0	1.350
-75.0	2.890	-43.5	19.73	-12.0	964.2	19.5	113.4	51.0	10.39	82.5	1.088
-73.5	3.193	-42.0	22.25	-10.5	1253	21.0	90.09	52.5	9.794	84.0	0.8488
-72.0	3.569	-40.5	23.66	-9.0	1520	22.5	75.38	54.0	9.020	85.5	0.6372
-70.5	3.921	-39.0	26.09	-7.5	1751	24.0	65.30	55.5	8.287	87.0	0.4782
-69.0	4.321	-37.5	29.14	-6.0	1934	25.5	57.50	57.0	7.655	88.5	0.3657
-67.5	4.709	-36.0	31.25	-4.5	2069	27.0	50.79	58.5	7.095	90.0	0.4081
-66.0	5.095	-34.5	33.51	-3.0	2169	28.5	45.35	60.0	6.558		
-64.5	5.478	-33.0	36.69	-1.5	2225	30.0	40.81	61.5	6.100		
-63.0	5.868	-31.5	40.65	0.0	2228	31.5	36.82	63.0	5.591		
-61.5	6.170	-30.0	45.01	1.5	2178	33.0	33.29	64.5	5.148		
-60.0	6.724	-28.5	50.23	3.0	2082	34.5	30.85	66.0	4.754		

Electricity Parameter:

Current I: 0.1000A Power: 3.420W  
 Voltage V: 34.20V PF: 1.000

Optical Parameter (Distance=2.410m):

Equivalent Luminous flux:  $\Phi_{eff}=371.5lm$  Efficiency:  $Eff=108.65lm/W$   
 Diffuse angle:  $\theta(25\%): 27.7deg \theta(50\%): 21.4deg \theta(75\%): 14.8deg \theta(50\%): 21.4deg$   
 Diffuse angle:  $\theta(25\%): 27.7deg \theta(50\%): 21.4deg \theta(75\%): 14.8deg \theta(50\%): 21.4deg$   
 $I_{max}=2233cd (C=0.0deg, G=-0.5deg)$  C0-180Plane  $I_{max}=2233cd(G=-0.5deg)$   
 C0-180Plane  $I_0=2228cd$

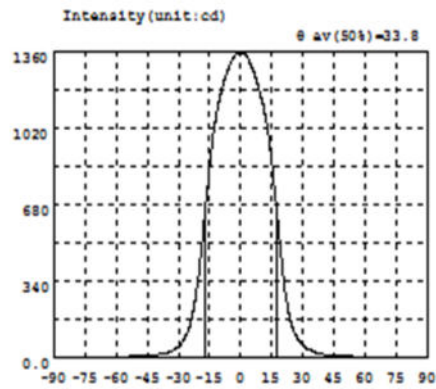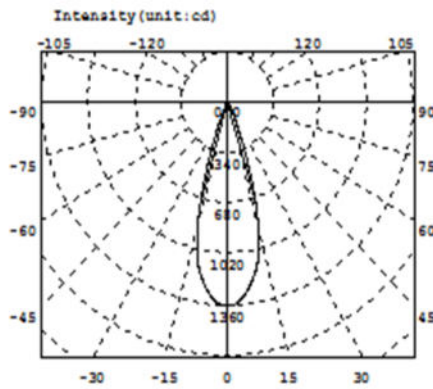

Intensity data: (deg , cd) CO-180

A	I	A	I	A	I	A	I	A	I	A	I
-90.0	0.3439	-58.5	6.720	-27.0	89.07	4.5	1309	36.0	26.07	67.5	4.469
-88.5	0.4078	-57.0	7.186	-25.5	119.2	6.0	1274	37.5	21.19	69.0	4.148
-87.0	0.6117	-55.5	7.594	-24.0	164.7	7.5	1231	39.0	18.15	70.5	3.835
-85.5	0.8518	-54.0	8.380	-22.5	231.4	9.0	1183	40.5	16.06	72.0	3.513
-84.0	1.120	-52.5	8.699	-21.0	319.1	10.5	1131	42.0	14.69	73.5	3.209
-82.5	1.415	-51.0	9.346	-19.5	432.7	12.0	1065	43.5	14.71	75.0	2.940
-81.0	1.700	-49.5	10.08	-18.0	569.1	13.5	974.9	45.0	13.63	76.5	2.628
-79.5	2.009	-48.0	10.90	-16.5	714.7	15.0	860.3	46.5	12.27	78.0	2.309
-78.0	2.355	-46.5	12.13	-15.0	851.4	16.5	728.7	48.0	10.92	79.5	2.014
-76.5	2.677	-45.0	13.23	-13.5	971.0	18.0	589.1	49.5	10.11	81.0	1.699
-75.0	3.049	-43.5	14.36	-12.0	1067	19.5	449.6	51.0	9.595	82.5	1.354
-73.5	3.384	-42.0	15.16	-10.5	1139	21.0	319.0	52.5	9.028	84.0	1.025
-72.0	3.697	-40.5	16.23	-9.0	1193	22.5	227.5	54.0	8.317	85.5	0.7206
-70.5	4.001	-39.0	17.81	-7.5	1244	24.0	162.9	55.5	7.769	87.0	0.4871
-69.0	4.267	-37.5	19.84	-6.0	1284	25.5	120.3	57.0	7.289	88.5	0.3151
-67.5	4.537	-36.0	22.71	-4.5	1315	27.0	91.86	58.5	6.713	90.0	0.2240
-66.0	4.789	-34.5	26.94	-3.0	1341	28.5	71.55	60.0	6.235		
-64.5	5.019	-33.0	32.93	-1.5	1352	30.0	56.94	61.5	5.821		
-63.0	5.401	-31.5	41.35	0.0	1354	31.5	46.36	63.0	5.455		
-61.5	5.776	-30.0	52.54	1.5	1350	33.0	39.62	64.5	5.119		
-60.0	6.200	-28.5	66.04	3.0	1336	34.5	32.00	66.0	4.786		



Electricity Parameter:

Current I: 0.1000A      Power: 3.358W  
 Voltage V: 33.59V      PF: 1.000

Optical Parameter (Distance=2.559m):

Equivalent Luminous flux:  $\Phi_{eff} = 457.71\text{lm}$       Efficiency:  $Eff = 136.33\text{lm/W}$   
 Diffuse angle: @ (25%) : 41.4deg @ (50%) : 33.8deg @ (75%) : 25.6deg @ (50%) : 33.8deg  
 Diffuse angle: @ (25%) : 41.4deg @ (50%) : 33.8deg @ (75%) : 25.6deg @ (50%) : 33.8deg  
 I<sub>max</sub>=1354cd (C=0.0deg, G=-0.5deg)      CO-180Plane I<sub>max</sub>= 1354cd(G=-0.5deg)  
 CO-180Plane I<sub>0</sub>= 1354cd



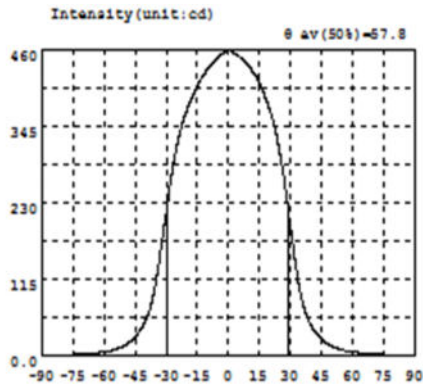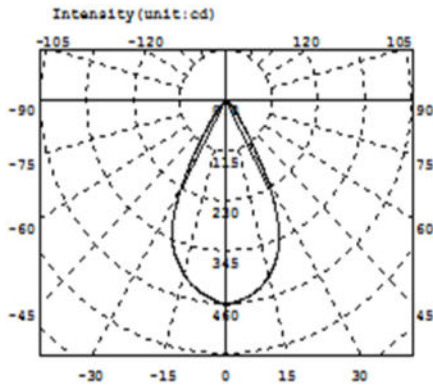

Intensity data: (deg , cd) C0-180

A	I	A	I	A	I	A	I	A	I	A	I
-90.0	0.3503	-58.5	7.652	-27.0	281.2	4.5	451.1	36.0	77.09	67.5	4.204
-88.5	0.3958	-57.0	8.620	-25.5	306.9	6.0	447.2	37.5	62.11	69.0	3.853
-87.0	0.5548	-55.5	9.689	-24.0	327.9	7.5	443.3	39.0	50.96	70.5	3.515
-85.5	0.7811	-54.0	11.05	-22.5	346.0	9.0	438.8	40.5	42.50	72.0	3.186
-84.0	1.030	-52.5	12.70	-21.0	360.8	10.5	432.8	42.0	35.92	73.5	2.869
-82.5	1.280	-51.0	14.81	-19.5	373.4	12.0	425.7	43.5	30.41	75.0	2.559
-81.0	1.551	-49.5	17.47	-18.0	383.8	13.5	417.7	45.0	25.67	76.5	2.272
-79.5	1.823	-48.0	20.60	-16.5	394.5	15.0	408.5	46.5	21.76	78.0	1.970
-78.0	2.106	-46.5	24.61	-15.0	405.0	16.5	397.9	48.0	18.55	79.5	1.676
-76.5	2.401	-45.0	29.53	-13.5	413.6	18.0	386.1	49.5	15.88	81.0	1.391
-75.0	2.683	-43.5	35.28	-12.0	421.4	19.5	373.4	51.0	13.64	82.5	1.127
-73.5	2.990	-42.0	41.74	-10.5	428.4	21.0	358.7	52.5	11.88	84.0	0.8575
-72.0	3.297	-40.5	50.07	-9.0	434.2	22.5	341.1	54.0	10.48	85.5	0.6083
-70.5	3.616	-39.0	60.73	-7.5	439.0	24.0	317.3	55.5	9.221	87.0	0.4144
-69.0	3.943	-37.5	75.42	-6.0	443.8	25.5	291.5	57.0	8.206	88.5	0.3413
-67.5	4.294	-36.0	95.50	-4.5	448.7	27.0	261.7	58.5	7.334	90.0	0.2949
-66.0	4.661	-34.5	121.1	-3.0	453.7	28.5	227.8	60.0	6.555		
-64.5	5.103	-33.0	151.2	-1.5	457.7	30.0	191.9	61.5	5.932		
-63.0	5.560	-31.5	184.7	0.0	459.5	31.5	156.3	63.0	5.423		
-61.5	6.128	-30.0	215.8	1.5	457.8	33.0	124.1	64.5	4.976		
-60.0	6.795	-28.5	250.7	3.0	454.1	34.5	97.33	66.0	4.569		

**Electricity Parameter:**

Current I: 0.1000A      Power: 0.3400W  
 Voltage V: 34.00V      PF: 1.000

**Optical Parameter (Distance=2.410m):**

Equivalent Luminous flux:  $\Phi_{\text{eff}}=399.91\text{lm}$       Efficiency:  $\text{Eff}=1176.45\text{lm/W}$   
 Diffuse angle:       $\theta(25\%): 68.2\text{deg}$   $\theta(50\%): 57.8\text{deg}$   $\theta(75\%): 44.8\text{deg}$   $\theta(50\%): 57.8\text{deg}$   
 Diffuse angle:       $\theta(25\%): 68.2\text{deg}$   $\theta(50\%): 57.8\text{deg}$   $\theta(75\%): 44.8\text{deg}$   $\theta(50\%): 57.8\text{deg}$   
 $\text{I}_{\text{max}}=459.5\text{cd}$  ( $C=0.0\text{deg}, G=0.0\text{deg}$ )      C0-180Plane  $\text{I}_{\text{max}}= 459.5\text{cd}(G=0.0\text{deg})$   
    C0-180Plane  $\text{I}_0= 459.5\text{cd}$

		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2			Judgment	Remarks
1.Size	diameter	110			109.72	109.77				Test environment: In 20 °C -25 °C environment to achieve thermal equilibrium after the test.
	height	32			31.895	31.9				
	thickness	3			2.97	2.93				
Gate shear can not affect the appearance of the lamp										
See attachment "Appearance Inspection Standards"										

2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	OK
			No stains	No stains	No stains	No stains	

3.Material	PC			Color	Transparent		OK
------------	----	--	--	-------	-------------	--	----

4.Optical index	Testing LED	CREE 1840						
	The recommended size and power rating of the LED light source recommended for this lens should be comparable to the source of the test, if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.							
	FWHM	See light distribution curve						
	angle		10.9	10.8				
	K-value		16.58	16.56				
	Efficiency		77.59%	78.21%				
Facula	See the signature sample							

Comprehensive judgment	Qualified						
------------------------	-----------	--	--	--	--	--	--

Remarks:

1、 Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.

2、 Ambient temperature on the size of the product refer to the table on the right

**PC product size changes with temperature table**

Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm
0	0.00	0.00	0.00	0.00	0.00	0.00
10	0.05	0.08	0.12	0.15	0.18	0.22
20	0.08	0.13	0.18	0.25	0.32	0.40
30	0.10	0.18	0.25	0.35	0.48	0.58
40	0.12	0.22	0.30	0.42	0.55	0.68

1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.
2. Try to avoid touching the total reflection surface when taking the lens.
3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).
4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.

		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2			Judgment	Remarks
1.Size	diameter	110			109.88	109.84				Test environment: In 20 °C -25 °C environment to achieve thermal equilibrium after the test.
	height	32			31.9	31.9				
	thickness	3			2.99	2.97				
Gate shear can not affect the appearance of the lamp										
See attachment "Appearance Inspection Standards"										

2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	OK
			No stains	No stains	No stains	No stains	

3.Material	PC			Color	Transparent		OK
------------	----	--	--	-------	-------------	--	----

4.Optical index	Testing LED	CREE 1840					
	The recommended size and power rating of the LED light source recommended for this lens should be comparable to the source of the test, if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.						
	FWHM	See light distribution curve					
	angle		21.4	21.5			
	K-value		6.01	5.84			
	Efficiency		79.96%	79.85%			
Facula	See the signature sample						

Comprehensive judgment	Qualified						
------------------------	-----------	--	--	--	--	--	--

Remarks:

1、Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.

2、Ambient temperature on the size of the product refer to the table on the right

**PC product size changes with temperature table**

Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm
0	0.00	0.00	0.00	0.00	0.00	0.00
10	0.05	0.08	0.12	0.15	0.18	0.22
20	0.08	0.12	0.18	0.25	0.32	0.40
30	0.10	0.15	0.22	0.30	0.38	0.48
40	0.12	0.18	0.28	0.38	0.48	0.60

1. Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.
2. Try to avoid touching the total reflection surface when taking the lens.
3. The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).
4. The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.



		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2			Judgment	Remarks
1.Size	diameter	110			110.02	109.89				Test environment: In 20 °C -25 °C environment to achieve thermal equilibrium after the test.
	height	32			32.03	32.04				
	thickness	3			3.04	3.06				
Gate shear can not affect the appearance of the lamp										
See attachment "Appearance Inspection Standards"										

2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	OK
			No stains	No stains	No stains	No stains	

3.Material	PC			Color	Transparent		OK
------------	----	--	--	-------	-------------	--	----


4.Optical index	Testing LED	CREE 1840						
	The recommended size and power rating of the LED light source recommended for this lens should be comparable to the source of the test, if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.							
	FWHM	See light distribution curve						
	angle		33.8	33.6				
	K-value		2.96	2.93				
	Efficiency		86.39%	86.52%				
Facula	See the signature sample							

Comprehensive judgment	Qualified						
------------------------	-----------	--	--	--	--	--	--

Remarks:

- Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.
- Ambient temperature on the size of the product refer to the table on the right

### PC product size changes with temperature table

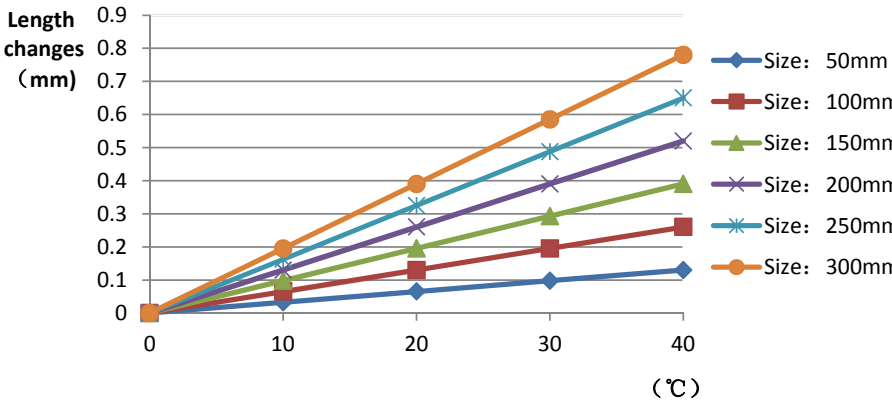

Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm
0	0.00	0.00	0.00	0.00	0.00	0.00
10	0.05	0.08	0.10	0.12	0.15	0.18
20	0.08	0.12	0.15	0.18	0.22	0.28
30	0.10	0.15	0.20	0.25	0.30	0.38
40	0.12	0.18	0.25	0.32	0.38	0.48

- Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.
- Try to avoid touching the total reflection surface when taking the lens.
- The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).
- The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.

		Standard size	Upper Size limit	Lower size limit	Test result1	Test result2			Judgment	Remarks
1.Size	diameter	110			109.89	109.99				Test environment: In 20 °C -25 °C environment to achieve thermal equilibrium after the test.
	height	32			32.085	32.085				
	thickness	3			3.04	2.94				
Gate shear can not affect the appearance of the lamp										
See attachment "Appearance Inspection Standards"										

2.Appearance Quality	See attachment "Appearance Inspection Standards"	E	No burr	No burr	No burr	No burr	OK
			No stains	No stains	No stains	No stains	

3.Material	PC			Color	Transparent		OK
------------	----	--	--	-------	-------------	--	----

4.Optical index	Testing LED	CREE 1840									
	The recommended size and power rating of the LED light source recommended for this lens should be comparable to the source of the test, if it is required to be out of range. According to the heat dissipation capability of the lamp and the actual conditions of the use environment, the lens should be fully tested and tested to prevent the lens life.										
	FWHM	See light distribution curve									
	angle			57.8	57.8						
	K-value										
	Efficiency			82.20%	82.20%						
Facula	See the signature sample										

Comprehensive judgment	Qualified									
------------------------	-----------	--	--	--	--	--	--	--	--	--


Remarks:

- Tool Number: V-Vernier Caliper 2D-Quadratic H-Height Gauge M-Tool Microscope P-Needle T-Thick Gauge R-Radius Gauge E-Visual.
- Ambient temperature on the size of the product refer to the table on the right

### PC product size changes with temperature table

Temperature (°C)	50mm	100mm	150mm	200mm	250mm	300mm
0	0.00	0.00	0.00	0.00	0.00	0.00
10	0.05	0.10	0.15	0.20	0.25	0.30
20	0.10	0.15	0.20	0.25	0.35	0.40
30	0.15	0.20	0.25	0.35	0.45	0.55
40	0.20	0.25	0.35	0.45	0.60	0.70





- Please wear clean gloves during the lens assembly process to prevent the lens surface from being contaminated.
- Try to avoid touching the total reflection surface when taking the lens.
- The lens surface is contaminated. Only use a soft cotton cloth dipped in analytically pure neutral solvent to wipe gently. Do not wipe with industrial solvents (alcohol, isopropanol, acetone, ether, toluene, xylene, carbon tetrachloride, MMA Body, etc.).
- The working temperature of the lens should be within the temperature resistance limit of the lens material. Exceeding the temperature resistance limit will cause the lens to crack or melt and affect the service life of the lens. It is recommended that the upper surface temperature of the LED colloid should be less than 120 degrees.

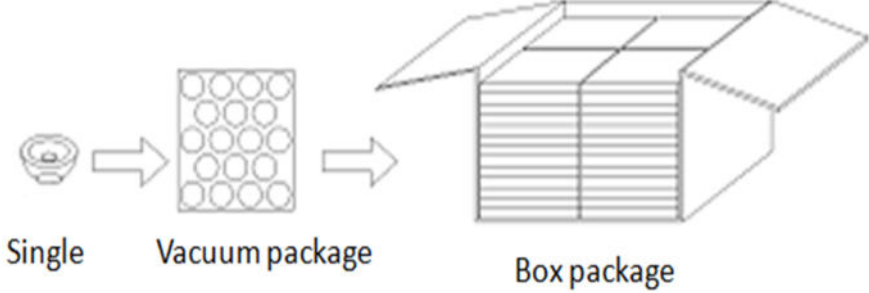PN		HK-110@32-15-D14-20-1g-1		Product Name	HK 110@32-15° lens		
Product material		PC		Customer			
Package diagram		 <p style="text-align: center;">Single      Vacuum package      Box package</p>					
Product packing				A/ Box			pcs/Layer
				Layer/Box			A/ Carton
Packaging Materials	NO.	Part No	Part name	Size	Dosage	Unit	Remarks
	1		Blister box	23cm*21cm			BAG
	2	2.08.0001	PE film	30cm*30cm			PCS
	3	2.06.0005	Reel label paper	6.2cm*8cm			PCS
	4	2.06.0005	Box label paper	6.2cm*9.2cm			PCS
	5	2.06.0003	big plate	46.8cm*42.8cm			PCS
	6	2.06.0015	big flat carton	48cm*44cm*19cm			PCS
Remarks	The loose packing is not subject to this specification. Customer's requirements shall prevail						

Special notice

When glue pass through holes, columns and other structures, or part of the thin structure, will form a weld line. The product which uses multi-point injection welding line will appear because of the combination of sol, as shown below:

Syntner

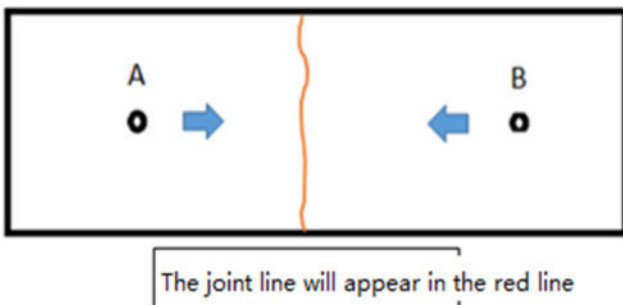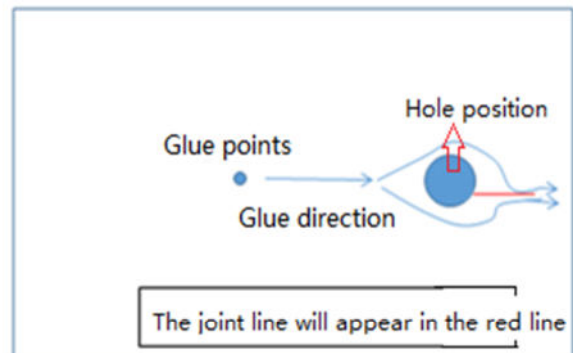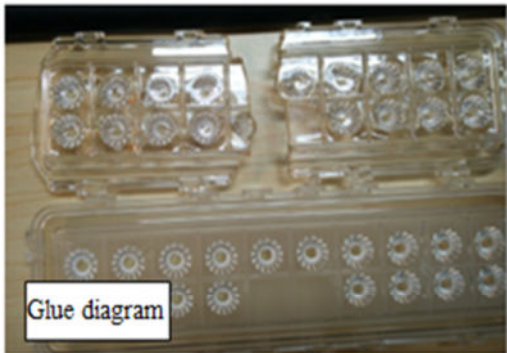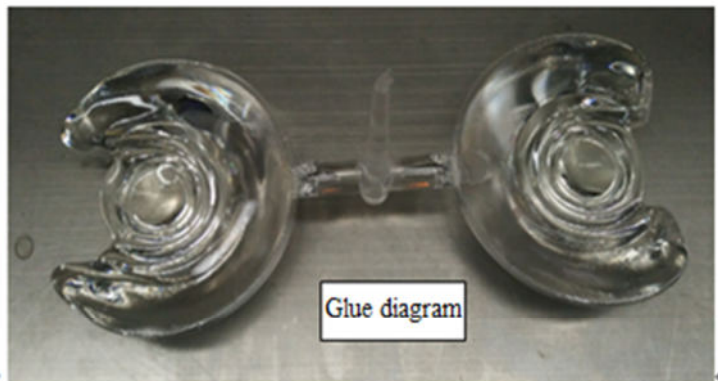

Please note :

The appearance of lines in the structure of the product as well as at the screw hole is a normal phenomenon, will not affect the actual use of the product, and can not be avoided at this stage.

## Appearance inspection standards

### 1 Operating procedures

#### 1.1.1 Sampling standards, sampling plan and AQL

Test level : GB/T2828.1-2012 The first part is according to the acceptance quality limit (AQL) retrieval batch inspection sampling plan, general inspection level II level, CR class defect coefficient 0, MA defect rejection level AQL = 0.65, MI class defect rejection level AQL = 1.0; defect level please see 5.4.

#### 2 Code table

Code	Code description	Unit	Code		Code description	Unit
N	Amount/pcs	pcs	D		Diameter	mm
L	Length	mm	H		Depth	mm
W	Width	mm	DS		Distance	mm
S	Proportion	mm <sup>2</sup>	SS		Offset	mm

### 3 Test conditions

3.1 Sight distance and working hours: Sight distance should be 30-35cm, each side of the inspection time does not exceed 12s, the visual angle of 45-135 degrees;

3.2 Light: 2x40w cool white fluorescent lamp, the light source is 500-550mm away from the lens surface; in order to make the appearance defect can be correctly recognized, the illumination should be 500-1000Lux, and the observation time is 10 seconds.

3.3 Visual inspection staff should be 1.0 (including corrected visual acuity) above, no color blindness, color weakness.

### 4 Appearance inspection standards

Test items	Judging standard	Inspection equipment	Defect level		
		Testing method	MI	MA	CR
Check the sample	When start the machine and process, all products have to check the appearance of the sample, the appearance of the sample is divided into qualified samples and limited samples.	Sample comparison , visual			
	1: Qualified sample refers to the appearance and structure standard of the product which recognized by the client, the sample size should be confirmed before mass production;				



	2: The limited sample refers to the limit of a particular exceptionally developed sample. Limit the sample only for its specific point of exception to confirm; The priority is higher than the other criteria in this table. When there is a limited sample, the limit sample shall prevail.				
Raw edge	Not allowed to affect the size and assembly	Visual, point card		√	
Scratch	1: Non-optical surface and non-exposed surface scratches should be visually insignificant and the length is less than 1/10 of the maximum surface size.	Visual, point card, calipers		√	
Fingerprint	Fingerprints are not allowed on all products	Visual		√	
Foreign objects, black spots, white spots	The product may not be attached to foreign objects, including oil, fiber, dregs of water gap and so on				√
Deformation	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces.	Visual, feeler			√
Poor ejection	Products may not appear bad ejection, including no convex top, thimble printed on the assembly surface shall not be higher than the product surface, non-assembled surface thimble height should not exceed the product size tolerances; thimble printing should be less than the product surface and no more than 0.3; thimble surface treatment should be consistent with the product side.	Visual, point card		√	
	Ejection strain: the optical surface and the appearance of the exposed surface after assembly are not allowed to have a strain, and the structural surface does not allow visual obvious strain.				
Insufficient filling	Insufficient filling shall not affect the appearance of the assembly and the exposed surfaces , The signature sample shall prevail.	Visual, point card		√	
Shrink	When the entire surface of the product shrinks, the optical properties and dimensions must meet the requirements, and the visual will not significantly affect the appearance.Part shrink reference point defects	Visual, point card		√	
Flow marks、Welding line	1 : Product does not allow the presence of flow marks and welding lines unless the structure can not be avoided;	Visual		√	
	2: The remaining flow marks shall not appear in the optical surface, a single L ≤ 10mm, no more than two				

Bubble	No bubbles are allowed	Visual		√	
Foreign objects, black spots, white spots	Not obvious or $D \leq 0.3\text{mm}$ black spots and foreign bodies in the area of 100x100mm not more than 1; Exceeded foreign matter black spots is judged bad.	Visual, point card	√		
Damaged	No damage is allowed	Visual			√
Cold glue	Optical surface may not have cold glue, non-optical surface cold glue should meet the visual is not obvious.	Visual	√		
Bad incision	1: Do not affect the product size, shall not penetrate the optical surface, the cut should be smooth;	Visual			√
	2: Laser cutting products, the optical surface burns shall not occur after the processing is completed. Beading must not affect product installation				
	3: Three molds and hot runner gate shall not appear residue.				
Scrub	Scrub surface should be uniform, off the scrub phenomenon should not be obvious , A single off scrub imprint requires $D \leq 1\text{ mm}$ and no more than 1 area within a 50x50 mm area	Visual		√	